Thermoplastics pipes and fittings with profiled outer and smooth inner surfaces

Part 1: Dimensions

16961-1

ICS 23.040.20; 23.040.45

Supersedes February 1989 edition.

Rohre und Formstücke aus thermoplastischen Kunststoffen mit profilierter Wandung und glatter Rohrinnenfläche – Teil 1: Maße

In keeping with current practice in standards published by the International Organization for Standardization (ISO), a comma has been used throughout as the decimal marker.

Contents

Pag	је			Page
Foreword	1	5.1.3	Length	. 5
1 Scope	1	5.1.4	Profile	. 5
2 Normative references	2	5.1.5	Designation	. 5
3 Concepts	2	5.2 F	Fittings	. 5
3.1 Nominal diameter	2	5.2.1	General	. 5
3.2 Outside diameter	2	5.2.2	Gusseted bends	. 6
4 Pipe series	2	5.2.3	45° branches	. 7
5 Dimensions and designation	2	5.2.4	Transition pipes	. 9
5.1 Pipes	2	5.2.5	PE-HD adapters	.10
5.1.1 Inside diameter	2	6 Jo	ints	.11
5.1.2 Outside pipe diameter	5			

Foreword

This standard has been prepared by Technical Committee *Profilierte Rohre aus thermoplastischen Kunst*stoffen mit glatter Innenwand of the *Normenausschuss Kunststoffe* (Plastics Standards Committee).

Amendments

This standard differs from the February 1989 edition in that specifications for outside diameters have been included and the standard has been revised in form and substance.

Previous editions

DIN 16961-1: 1977-09, 1989-02.

All dimensions are in millimetres.

1 Scope

This standard specifies dimensions and tolerances for thermoplastics pipes and fittings with profiled outer and smooth inner surfaces.

For the purposes of this standard, profiled pipes are those with profiled outside surfaces, flanged pipes, helically wound pipes, and pipes with foamed inserts in their walls.

NOTE: Fittings manufactured differently may also be used in pipework.

Pipes manufactured in accordance with this standard may also be used as components in process engineering.

NOTE: Any relevant European Standards shall also be observed.

Continued on pages 2 to 11.

Translation by DIN-Sprachendienst.

In case of doubt, the German-language original should be consulted as the authoritative text.

DIN 16961-1:2000-03

Normative references

This standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the titles of the publications are listed below. For dated references, subsequent amendments to or revisions of any of these publications apply to this standard only when incorporated in it by amendment or revision. For undated references, the latest edition of the publication referred to applies.

DIN 323-1 Preferred numbers and preferred number series - Basic, calculated and rounded values

DIN 16961-2 Thermoplastics pipes and fittings with profiled outer and smooth inner surfaces - Technical delivery conditions

DIN 19537-1 High-density polyethylene (PE-HD) pipes and fittings for drains and sewers - Dimensions

DVS-Richtlinie 2207-1 Schweißen von thermplastischen Kunststoffen – Heizelementschweißen von Rohren, Rohrleitungsteilen und Tafeln aus PE-HD (Welding of high-density polyethylene pipes and pipe fittings for gas and water pipework)1)

DVS-Richtlinie 2209-1 Schweißen von thermoplastischen Kunststoffen - Extrusionsschweißen - Verfahren. Merkmale (Extrusion welding of thermoplastics - Welding procedure and characteristics)1)

Concepts

3.1 Nominal diameter

The diameter, in millimetres, on which the pipe size is based (outside or inside diameter); designated by d_n .

3.2 Outside diameter

The distance between any two points on the outer circumference of the pipe or spigot end of a fitting, located on a diagonal across the pipe bore.

Pipe series

Pipe classification is based on the ring stiffness, S_{R24} , as specified in table 1, with the ring stiffness values being based on the series R 10 as in DIN 323-1.

5 2 3 4 6 Pipe series no. Minimum ring 31,5 63 125

4

2

Table 1: Ring stiffness

8

16

7

11

 $S_{
m R24}$, is a parameter required in pipe design which cannot be accurately calculated for pipes with profiled outer surfaces, for flanged pipes, or for pipes made of composite materials. In these cases, S_{R24} is to be determined as in DIN 16961-2.

5 Dimensions and designation

5.1 Pipes

5.1.1 Inside diameter

Pipe sizes are based on the inside diameter, d_i , corresponding to series R 10 as in DIN 323-1 for inside diameters from 100 mm to 630 mm, and to series R 20 as in DIN 323-1 for inside diameters from 710 mm to 2800 mm. Commonly used inside diameters not corresponding to either series R 10 or R 20 have been identified by a footnote in table 2.

NOTE: Exact dimensions shall be as specified in the relevant company standard.

stiffness, $S_{
m R24}$,

in kN/m²


Pipes shall be manufactured with socket and spigot end (type I or II) or with plain ends (type III). Dimensions d_i , d_a , l_1 and l_2 shall be at the manufacturer's discretion.

The designs shown in figure 1 are for illustrative purposes only, but the dimensions shall be as specified in table 2.

Obtainable from Verlag für Schweißen und verwandte Verfahren (DVS-Verlag) GmbH, Postfach 10 19 65, 40010 Düsseldorf, Germany.

Page 3 DIN 16961-1 : 2000-03


Type I Socket pipe for welding

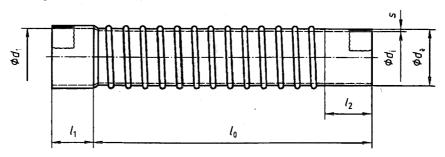

Type II Socket pipe with seal

Type III

Pipe with plain ends



The illustration shows a type III pipe. A greater wall thickness at the pipe ends is permissible.

In both illustrations,

- $d_{\rm i}$ is the pipe inside diameter;
- $d_{\scriptscriptstyle \mathrm{a}}$ is the pipe outside diameter;
- d_1 is the socket inside diameter;
- is the overall length;
- is the socket length;
- is the spigot length

Figure 1: Pipes (notation)

Table 2: Tolerances on pipe inside diameter

Table 2: Tolerances on pipe inside diameter							
Nominal size	Pipe inside diameter, $d_{ m i}$	Lower deviation	Limit deviations ²) Upper deviation				
DN		for series 1 to 7	for series 1 to 4	for series 5 to 7			
100	100	- 3	+ 1	+ 2			
125	125	- 3	+ 2	+ 2			
150	150¹)	- 4	+ 2	+ 3			
200	200	- 5	+ 3	+ 4			
250	250	- 6	+ 4	+ 5			
300	300¹)	- 8	+ 4	+ 6			
315	315	- 8	+ 5	+ 6			
350	350¹)	- 9	+ 5	+ 7			
400	400	-10	+ 6	+ 8			
450	450¹)	-11	+ 7	+ 9			
500	500	-13	+ 7	+10			
600	600¹)	-15	+ 9	+12			
630	630	-16	+ 9	+13			
700	700 ¹)	- 18	+10	+14			
800	800	- 20	+12	+16			
900	900	- 23	+13	+18			
1 000	1 000	- 25	+15	+20			
1 200	1 200 ¹)	- 30	+ 18	+24			
1 400	1 400	- 35	+ 21	+28			
1 500	1 500 ¹)	- 38	+ 22	+30			
1 600	1 600	- 40	+ 24	+32			
1 800	1 800	- 45	+27	+36			
2 000	2 000	- 50	+30	+40			
2 200	2 200 ¹)	- 55	+33	+44			
2 240	2 240	- 56	+34	+45			
2 400	2 400 ¹)	- 60	+36	+48			
2 500	2500	- 63	+37	+50			
2 600	2600¹)	- 65	+39	+52			
2 800	2800	- 70	+42	-			
3 000	3000¹)	- 75	+45	+60			
3 500	3500	- 87	+52	+70			
3 600	3600	- 90	+54	+72			

¹⁾ Does not correspond with series R 10 or R 20 as in DIN 323-1.

for pipe series 1 to 4: $d - 0.025 d_i$ up to d + 0.015 d; for pipe series 5 to 7: $d - 0.025 d_i$ up to d + 0.02 d.

²) Limit deviations have been calculated as follows:

DIN 16961-1: 2000-03

5.1.2 Outside diameter

Table 3: Tolerances on pipe outside diameter

Nominal size	Planting	Limit d	eviation
DN	Pipe outside diameter, d_{a}	for pipes with foamed inserts	for pipes with profiled outer surface
100	110	± 5	± 10
110	110	± 5	±10
125	125	± 5	± 10
140	140	± 5	±10
150	160	± 5	±10
160	160	± 5	±10
180	180	± 5	±10
200	200	± 5	±10
225	225	± 5	±10
250	250	± 5	±10
300	315	± 0,02 d _a	±0,04 d _a
400	400	±0,02 d _a	± 0,04 d _a
500	500	±0,02 d _a	± 0,04 d _a
600	630	± 15	±30
700	710	±15	±30
800	800	±15	±30
900	900	±15	±30
1 000	1 000	±15	±30
1 200	1 200	±15	±30

5.1.3 Length

Pipes shall be supplied in overall lengths of 2 m, 3 m, 4 m, 5 m, 6 m, 10 m and 12 m, or, by agreement, in approximate and fixed lengths. Ends shall be cut square to the pipe axis.

Table 4: Limit deviations for pipe length

Overall length, l_0	Limit deviations at (23 ± 2) °C, in mm
Approximate length	± 100
Fixed length (up to 12 m)	+ 50 0

5.1.4 Profile

The type of profile shall be at the manufacturer's discretion and shall be described in the product data sheet. The surface profile shall be selected to suit the ring stiffness determined in accordance with DIN 16961-2.

5.1.5 Designation

Designation of a series 4 type I PE-HD pipe, of size DN 1000, with an overall length of 6 m:

5.2 Fittings


5.2.1 General

Fittings shall be made by joining pipe segments, and their ring stiffness shall be at least equal to that of the pipe to which they are joined. In the case of socket fittings, this applies for the socket with the spigot end inserted. The dimensions of type I, II or III fittings made by welding pipe sections shall be as in subclauses 5.2.2 to 5.2.5. Figures 2 to 4 are for illustrative purposes only and do not show the wall profile of the fittings, but the dimensions shall be as specified in tables 5 to 8.

DIN 16961-1: 2000-03

5.2.2 Gusseted bends

Type I gusseted bend, with socket for welding Type II gusseted bend, with socket and seal Type III gusseted bend, with plain ends

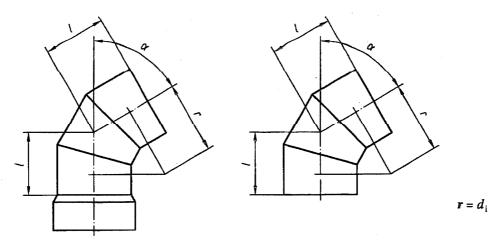

The illustration shows a type I gusseted bend.

The illustration shows a type III gusseted bend.

Figure 2: Gusseted bends

Designation of a series 3 type I PE-HD gusseted bend (SB) of size DN 1000, with $\alpha = 30^{\circ}$:

Bend DIN 19961 - SB - DN 1000 - 30 - 3 I - PE-HD

Table 5: Dimensions for gusseted bends

	_	·	ic o. Dillici						
			Dimension I (approx.)						
Nominal	Pipe inside diameter,	Wall thick-	Number of segments						
size	$d_{\rm i}$	ness, t	2	2	3	3	4	4	
DN		α = 15°	α = 30°	α = 45°	α = 60°	α = 75°	α = 90°		
Belo	w 300		Made to order.						
300 315 350	300 315 350		40 42 45	85 90 98	125 132 145	175 185 205	230 245 270	300 315 350	
400 450 500	400 450 500	As speci- fied by the manufac- turer.	50 58 65	110 125 135	165 185 205	230 260 290	305 345 385	400 450 500	
600 630 700	600 630 700		80 83 90	160 168 185	245 260 290	345 365 405	460 485 535	600 630 700	
700 800 900	700 800 900		92 105 120	192 215 240	295 330 370	410 460 520	545 615 690	710 800 900	
1 000 1 200	1 000 1 200		130 160	265 320	415 495	575 695	770 920	1 000 1 200	
Ove	r 1200		<u> </u>	N	lade to orde	r.		3	

Page 7 DIN 16961-1 : 2000-03

5.2.3 45° branches

Type I branch, with socket for welding Type II branch, with socket and seal Type III branch, with plain ends

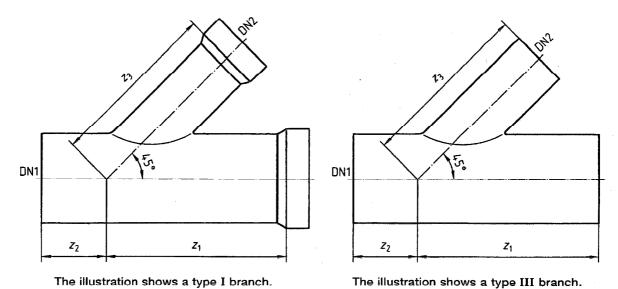


Figure 3: 45° branch

Designation of a series 4 type I PVC-U 45° branch (SEA) of size DN 1 = 600 and size DN 2 = 400: $Branch\ DIN\ 16961 - SEA - 600 - 400 - 4\ I - PVC-U$

Table 6: Dimensions for 45° branches


		1 able 6:	Dimensions to	r 45° branches		
Nominal size DN 1	Pipe inside diameter, d_{i1}^{1})	Nominal size DN 21)	Pipe inside diameter, $d_{ m i2}$	² 1 ≈	2 ₂ ≈	^z 3 ≈
Bel	Below 300			Made to order		
300 315 350	300 315 350	250 300 315 350	250 300 315 350	750	350	750
400 450	400 450	250 300 315 350 400 450	250 300 315 350 400 450	900	400	900
500	500	250 300 315 350 400 450 500	250 300 315 350 400 450 500	1 000	400	1 000
600 630	600 630	250 300 315 350 400 450 500 600	250 300 315 350 400 450 500 600 630	1 200	400	1 200
700 800	700 800	250 300 315 350 400 450 500 600 630 700	250 300 315 350 400 450 500 600 630 700 800	1 400	500	1400
Ove	er 800			Made to order.		
¹) DN 1 equa	to or greater that	an DN 2.			and the second s	
·						


Page 9 DIN 16961-1 : 2000-03

5.2.4 Transition pipes

111)

Type I transition pipe, with socket for welding Type II transition pipe, with socket and seal Type III transition pipe, with plain ends





The illustration shows a type I transition pipe.

The illustration shows a type III transition pipe.

Dimensions t_1 and t_2 shall be at the manufacturer's discretion.

Figure 4: Transition pipe

Designation of a type I series 4 PE-HD transition pipe (SR) of nominal size DN 1 = 400 and nominal size D2 = 500:

Transition pipe DIN 16961 – SR – $400 \times 500 - 4 I$ – PE-HD

Table 7: Dimensions for transition pipes

Nominal size DN 1	Pipe inside diameter, $d_{\scriptscriptstyle m II}$	Nominal size DN 2	Pipe inside diameter, d_{i2}	Dimension <i>l</i> (approx.)
В	elow 300		Made to order.	
300 315	300 315	400 400 500 500		350 700
400	400	500 600 630	500 600 630	350 700 700
500	500	600 630 700	600 630 700	350 350 750
600 630	600 630	700 800	700 800	400 750
700	700	800 900	800 900	350 750
800	800	900 1 000	900 1 000	350 750
C	ver 800	·····	Made to order.	

DIN 16961-1: 2000-03


5.2.5 PE-HD adapters


Type I adapter, with socket for welding

Type II adapter, with socket and seal

Type III adapter, with plain ends

PE-HD adapters shall be made from a pipe section with a nominal size or inside diameter as specified in table 2 and a PEGMS socket as specified in DIN 19537-1.

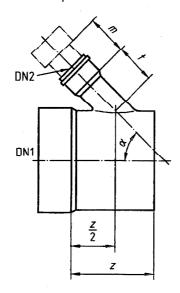

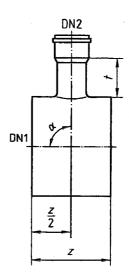

The illustration shows a type I adapter.

The illustration shows a type III adapter.

Dimension t shall be at the manufacturer's discretion.

Figure 5: PE-HD adapter (notation)

Designation of a series 4 type I PE-HD adapter with socket (SPA), of nominal size DN 1 = 800, fitted with a series 2 type II PEGMS socket of nominal size DN 2 = 200, welded to the adapter at an angle, α , of 45°:

Adapter DIN 16961 - SPA - 800 - 4 I - PE-HD - 45 - PEGMS - II 200 - 2

Table 8: Dimensions for adapters

Nominal size DN 1	Nominal size DN 2	Outside pipe diameter, d_i^1)	t ≈	m ≈	<i>2</i> ≈	α ≈
Nominal size as		110 125 125 140 160 180	300	300	500	Optional.
in table 2. 200 200 250 250 300 300	200 225 250 280 315 355	400	400	330	Optional	

6 Joints

Pipes and fittings shall be joined by welding (see figures 6 to 8 and 10) or by inserting a spigot end in a socket with a seal (see figure 9). Welding shall be in accordance with the specifications of DVS 2207-1 and DVS 2209-1.

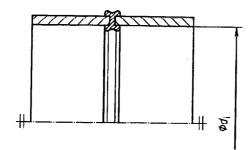


Figure 6: Heated tool butt weld

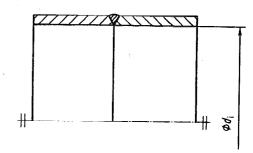


Figure 7: V extrusion butt weld (X weld permitted for larger sizes)




Figure 8: Socket extrusion weld (inner weld for size DN 800 or larger)




Figure 9: Push-in joint with seal (seal type to be selected by manufacturer)




Figure 10: Socket for resistance welding for DN 300 or larger